

Removal of Pollutants from Waste Foundry Sand by Chemical Washing Method

S. Balbay and C. Acikgoz

Abstract—The purpose of this research was to remove of metallic contaminant and other pollutants from waste foundry sand(WFS) by chemical washing method. Firstly, experimental investigation for removing of metallic contaminant and other pollutants from waste foundry sand(WFS) by using three different solutions 5 M HCl, 5 M H₂SO₄ and 5M NaOH. The extraction is carried out 3, 8 and 16 hours for each solution at 25 °C. After that, two - stage washing (successive washing with two different chemical) and triptych washing (successive washing with three different chemical) was applied to WFS. Functional group analysis of WFS and WFS after washing was done by using FT-IR. Results show the highest percentage of pollutant removal in H₂SO₄ – NaOH – HCl of triptych washing method.

Keywords— chemical washing, metallic and other pollutants, waste foundry sand

I. INTRODUCTION

Waste foundry sands represent the highest amount of solid wastes generated by foundries. Waste foundry sand (WFS) is a discarded material coming from ferrous and nonferrous metal-casting industry. Foundry sand typically consists of 85-95wt.% high-quality silica sand with uniform physical characteristics which is used by the foundry industry to create metal casting molds. Classification of foundry sands depends upon the type of binder systems used in metal casting. Two types of binder systems are generally used, and on the basis of that foundry sands are categorized as: clay-bonded sand (green sand) and chemically bonded sand[1]. Sodium silicate is used in foundries to bind sand grains by means of an appropriate acid, either directly such as CO₂, or indirectly with an organic ester, which hydrolyzes and subsequently gels the silicate sand mass. A gel network is prepared by acidifying concentrated sodium silicate (3.3ratio of SiO₂:Na₂O) solution. Sodium silicate solution, under acidic conditions is polymerized to silica and acts as an inorganic binder[2]. Foundries successfully recycle and reuse the sand many times. When the sand can no longer be reused in the foundry, it is removed from the foundry and is termed as waste foundry sand. Additionally, chemical composition of the WFS also depends on the type of metal

molded at the foundry. Several authors have reported the use of used-waste foundry sand in various civil engineering applications[3]. They have reported the use of used-waste foundry sand in various civil engineering applications such as highway applications, leaching aspect of usage of foundry sand, controlled low strength materials, concrete and concrete related products like bricks, blocks and paving stones, asphalt concrete[4]. In addition, the applications of waste foundry sand could be in following areas; barrier layers construction, embankments, flowable fills, road-way construction, agriculture, soil reinforcement/amendments, hot mix asphalt, portland cement manufacturing, mortars, traction material on snow and ice, vitrification of hazardous materials, smelting, rock wool manufacturing and fiberglass manufacturing[15]. However, the recycling of this waste is limited because its characteristics change significantly after use. This requirement poses a serious environmental problem due to not only the elevated volume produced but also the toxic substances found within the WFS, as the sand is contaminated by several dangerous chemical elements such as heavy metals (arsenic, cadmium, lead, and mercury) and organic compounds such as phenols [5].

The objective of this research is to remove of metallic contaminant and other pollutants from waste foundry sand(WFS) by chemical washing method.

II. MATERIAL AND METHODS

Waste foundry sand used for the experimental work were supplied by Kibaroglu Döküm Sanayi Ltd. Şti. in Turkey. The WFS is grayish in color with irregular shape. The particle size distribution of WFS was determined <1,18 mm. Firstly, the WFS was washed with distilled water and then dried overnight. 1 g of sample has been taken in beaker. Chemical washing studies of prepared WFS were performed at 25 °C. The dried WFS treated with 5 M hydrochloric acid (5 M HCl), 5 M sulphuric acid (5 M H₂SO₄), and 5 M sodium hydroxide (5 M NaOH) to remove of metallic contaminant and other pollutants, respectively. It has been well mixed by mechanical stirred at a speed of 300 rpm. Each experiment was carried out three times. The chemical treated WFS was washed with distilled water until the neutral pH was reached, and was filtered through over 0.45 µm membrane filters, then dried in an oven at 105 °C for 2

S. Balbay is with Bilecik Seyh Edebali University , Vocational School, Department of Chemical and Chemical Process Technologies,11030 BILECİK/TURKEY (e-mail: senay.balbay@bilecik.edu.tr).

C. Acikgoz was with Bilecik Seyh Edebali University, Faculty of Engineering, Department of Chemistry and Process Engineering, 11030 BILECİK/TURKEY (e-mail: caglayan.acikgoz@bilecik.edu.tr).

hours. The removal percentage of contaminants was calculated as follows:


$$\text{Removal (\%)} = \frac{(A_i - A_f)}{A_i} \times 100$$

where A_i and A_f are the initial and final sample amounts, respectively. pH was measured using a pH meter (Hanna HI 991001). Waste foundry sand has low absorption capacity and is non-plastic[15]. The functional group compositional analysis of WFS and WFS after washing samples was investigated using FT-IR spectrophotometry (Perkin Elmer, model spectrum 100, Bilecik, Turkey).

III. RESULTS AND DISCUSSION


The effect of washing time on the percentage of pollutant removal for 5 M HCl, 5 M H₂SO₄ and 5M NaOH solutions was studied. Chemical reactions involved in the washing studies by using three different solutions 5 M HCl, 5 M H₂SO₄ and 5M NaOH are grouped according to the following:

i) Reaction of sodium silicate with hydrochloric acid solution




Sodium silicate by adding dilute HCl, react through polycondensation reactions and lead to a silica gel by releasing water and NaCl (Eq. (1-2)) [16]-[17].

ii) Reaction of sodium silicate with sodium hydroxide solution



Attack of the siloxane bridges and disintegration of the silica [17] – [18].

iii) Reaction of sodium silicate with sulphuric acid solution



Acidification of the diluted sodium silicate solution via a reaction like the one below results in the formation of a semi solid network silicate gel (pH 10) as shown in Reaction (4) [19].

The washing times for HCl, H₂SO₄ and NaOH solutions were determined at 8 h, 16 h and 8 h, respectively (Fig.1). It was determined that the maximum removal percent as 13% with NaOH solution at 8 h washing time.

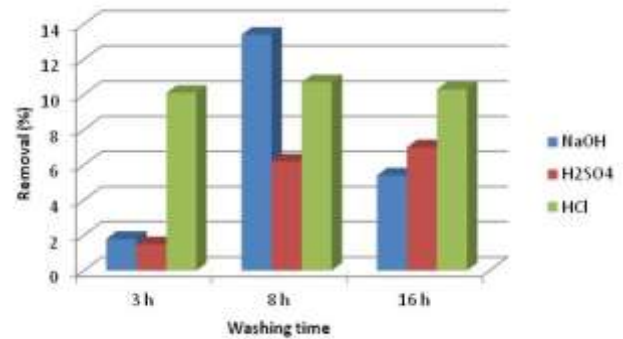


Fig 1. The effect of washing time of pollutant removal for per HCl, H₂SO₄ and NaOH (Solution concentration: 5 M, WFS amount: 1.0 g, Temperature: 25 °C)

The result of two - stage washing experimental studies were give in figure2. The highest removal percentage of pollutant was obtained in NaOH – HCl ambients of two - stage washing as 30%.

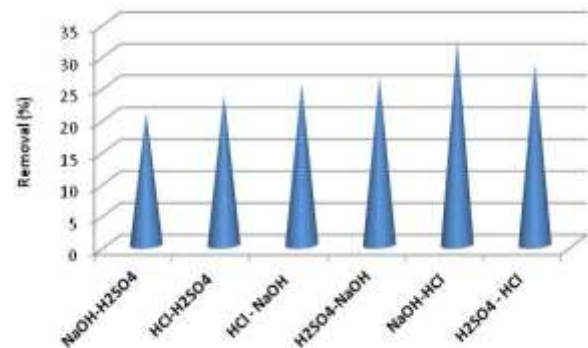


Fig 2. The effect of two - stage washing on pollutant removal (Solution concentration: 5 M, WFS amount: 1.0 g, Temperature: 25 °C)

Sodium silicate is very alkaline in nature having a pH ~12 [19]. Sodium silicate solution, under acidic conditions is polymerized to silica and acts as an inorganic binder [2]. According to reaction of sodium silicate with sulphuric acid solution, the silicate gel consists of a network of polymerized Si-O-Si-OH groups that traps water via solvation and hydrogen bonding forces (Eq. (4)). The structure of sodium silicate consists of silicate tetrahedral along with sodium that is not bonded into the structure and therefore can be washed out of the silicate gel that forms[19].

Silica is known to be more soluble in basic medium. A chemical reaction between the silica surface and the hydroxyl groups present in the basic solution could be consider by breaking the Si-O-Si leading to the formation of Si-OH and Si-O⁻ groups (Eq. (3)) [17].

The result of three-stage washing experimental studies were give in figure3. The highest removal percentage of pollutant was obtained in H₂SO₄ - NaOH – HCl ambients of triptych washing as 40%.

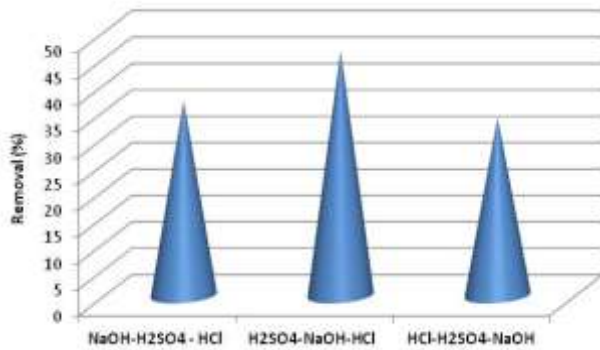


Fig 3. The effect of triptych washing on pollutant removal (Solution concentration: 5 M, WFS amount: 1.0 g. Temperature: 25 °C)

Chemical composition of the waste foundry sand depends on the type of metal molded at the foundry, type of binder and combustible used. The chemical composition of the foundry sand may influence its performance[1]. Silica sand is hydrophilic and consequently attracts water to its surface[15].

The effects of washing technique on chemical bonding in the WFS were studied using FTIR spectroscopy. Functional group analysis of used WFS and WFS after washing was done by using FT-IR. FTIR spectra of the WFS and WFS after washing samples are shown in Fig. 4-7. The peaks centered at 1070 and 495 cm⁻¹ correspond to the Si–O–Si bonds and were the most informative of the silica network structure. In contrast, for the OD silica powder, a strong–OH peak (less stretched) at 3390 cm⁻¹, indicated that a significant fraction of the Si atoms existed on the surface of the silica network structure as hydroxylated species[20].

The presence of the anchored propyl group was confirmed by C–H stretching vibrations that appeared at 2933 and 2875 cm⁻¹ [7]. Peaks in the spectral range at around of 1600 cm⁻¹ and 2300 cm⁻¹ are attributed to vibrations of carbon impurity atoms in the sample[8]. The presence of carbon in the WFS can be seen by two strong absorption bands at around 1619, 2921 and 2844 cm⁻¹ (see Fig. 4 and Table.1).

In H₂SO₄ - NaOH – HCl ambients of triptych washing wasn't observed Si-O-Si and - OH ligand metal complex from 1400 to 1450 cm⁻¹(Table.1 and Fig 4-7).

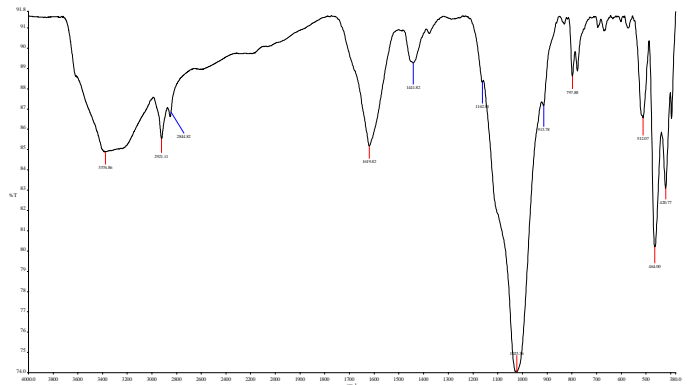


Fig 4. FT-IR spectrum of WFS



Fig 5. FT-IR spectrum of WFS in NaOH – HCl ambients of two - stage washing

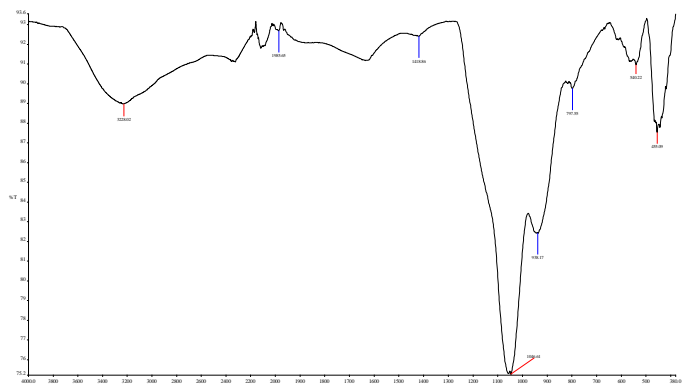


Fig 6. FT-IR spectrum of WFS in NaOH - H₂SO₄ – HCl ambients of triptych washing

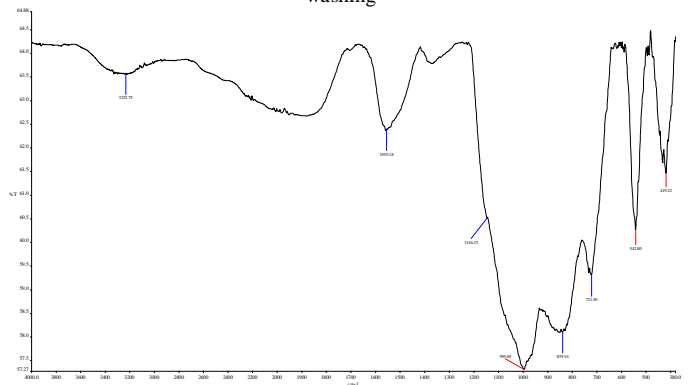


Fig 7. FT-IR spectrum of WFS in H₂SO₄ - NaOH – HCl ambients of triptych washing

Table 1. Attribution of FT-IR absorption for WFS and WFS after washing

Waste foundry sand (cm ⁻¹)	NaOH - HCl (cm ⁻¹)	NaOH - H ₂ SO ₄ - HCl (cm ⁻¹)	H ₂ SO ₄ - NaOH - HCl (cm ⁻¹)	Assignment
3376,86	3390,8			O-H stretching vibration of molecular water in the sample[6]
		3228,02	3232,75	Si - O - H bands [7]
2921,11				C-H stretching vibrations [7]
2844,82				C-H stretching vibrations [7]
	2163,79	1985,65		C ≡ C bands
1619,82	1624,05			C - O bands [8]
			1555,18	C = C bands [9]
1441,82	1441,82	1418,86		Si-O-Si and - OH ligand metal complex [10]
1162,01			1146,23	Si-O-Si anti-symmetric stretching of bridging oxygen atom within tetrahedra [11]- [12]
1023,36	1048,94	1046,61	995,05	Si-OH bands [14] - [7]
913,78	915,49	938,17		Si-O-Si symmetric stretch of bridging oxygen atoms between tetrahedra [13]
			839,16	Si-C stretching vibration[9]
797,88		797,55		Si-O-Si symmetric stretch of bridging oxygen atoms between tetrahedra [13]
	757,37		721,5	
	563,66			
	535,92	540,22	542,8	the rocking motion of Si-O-Si bridging oxygen which connects the various Qn species of silicates [8]
512,07				
464	466,62	455,09		
420,77			419,22	

IV. CONCLUSIONS

Removal of metallic contaminant and other pollutants from waste foundry sand (WFS) has been studied and experimental studies help to conclude reduction of metallic contaminant and other pollutants is much more better in case of H₂SO₄ - NaOH - HCl ambients of triptych washing and maximum reduction of metallic contaminant and other pollutants is 40%. The treated WFS may be reused in the foundry and various engineering applications such as rock wool manufacturing and fiberglass manufacturing.

REFERENCES

- [1] Kaur, G., Siddique, R., Rajor, A., "Properties of concrete containing fungal treated waste foundry sand", *Construction and Building Materials*, Vol. 29, pp. 82-87, July 2011
- [2] Miguel, E., R., Ippolito, J., A., Leytem, A., B., Porta, A., A., Noriega, B., R., B., Dungan, R., S., "Analysis of total metals in waste molding and core sands from ferrous and non-ferrous foundries", *Journal of Environmental Management*, Vol. 110, pp. 77-81, May 2012
- [3] Singh, G., Siddique, R., "Abrasion resistance and strength properties of concrete containing waste foundry sand (WFS)", *Construction and Building Materials*, Vol. 28, pp. 421-426, August 2011
- [4] Aggarwal, Y., Siddique, R., "Microstructure and properties of concrete using bottom ash and waste foundry sand as partial replacement of fine aggregates", *Construction and Building Materials*, Vol. 4, pp. 210-223, December 2013
- [5] Mastella, M., A., Gislou, E., S., Pelisser, F., Ricke, C., Silva, L., Angioletto, E., Montedo, O., R., K., "Mechanical and toxicological evaluation of concrete artifacts containing waste foundry sand", *Waste Management*, Vol. 34, pp. 1495-1500, February 2014
- [6] Stanley, R., Samson Nesaraj, A., "Effect of Surfactants on the Wet Chemical Synthesis of Silica Nanoparticles", *International Journal of Applied Science and Engineering*, Vol. 12, pp 9-21, October 2013
- [7] Khatiri, R., Reyhani, A., Mortazavi, S., Z., Hossainipour, M., "Preparation and characterization of Fe₃O₄ /SiO₂ / APTES core-shell nanoparticles", *Proceedings of the 4th International Conference on Nanostructures (ICNS4)*, pp. 1456- 1458, Kish Island, I.R. Iran, 2012
- [8] Shokri, B., Abbasi Firouzjah, M., Hosseini, S., I., "FTIR analysis of silicon dioxide thin film deposited by Metal organic-based PECVD", <http://www.ispc-conference.org/ispcproc/ispc19/791.pdf>
- [9] Uluçay, I, E., "Doğal Bileşikler Usnik Asit Ve Naringenin Silika-Jele Bağlanması Ve Metal Komplekslerinin Sentezlenmesi: Kati Faz Ekstraksiyon Özellikleri Ve Katalitik Aktivitelerinin İncelenmesi", M.S. thesis, Fen Bilimleri Enstitüsü, Kilis 7 Aralık Üniversitesi, Kilis, Turkey, 2013
- [10] Keleş, M., Serindağ, O., "Katı Desteğe Tutturulmuş Fosfin Ligandları Ve Metal Komplekslerinin Sentezlenmesi", *Ç.Ü Fen Bilimleri Enstitüsü Yıl:2008 Cilt:18-1*
- [11] Yıldızay, H., Gören, R., Yanık, G., "Alunit Mineralinin Jeopolimer Başlangıç Malzemesi Olarak Kullanımı", *AKU J. Sci. Eng.*, Vol. 14, pp. 219-224, Afyon, Turkey, 2014
- [12] ElBatal, F., H., Abdelghany, A., M., ElBatal, H., A., "Characterization by combined optical and FT infrared spectra of 3d-transition metal ions doped-bismuth silicate glasses and effects of gamma irradiation", *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*, Vol. 122, pp. 461-468, November 2013
- [13] ElBatal, H., A., Azooz, M., A., Khalil, E., M., A., A. Soltan Monem, A., Hamdy, Y., M., "Characterization of some bioglass-ceramics", *Materials Chemistry and Physics*, Vol. 80, pp. 599-609, November 2002
- [14] Mishra, L., Sharma, A., Vishwakarma, A., K., Jha, K., Jayasimhadri, M., Ratnam, B., V., Jang, K., Rao, A., S., Sinha, R., K., "White light emission and color tunability of dysprosium doped barium silicate glasses", *Journal of Luminescence*, Vol. 169, pp. 121-127, August 2015
- [15] Siddique R., Singh, G., "Utilization of waste foundry sand (WFS) in concrete manufacturing", *Resources, Conservation and Recycling*, Vol. 55, pp. 885-892, May 2011
- [16] Gözoğul, R., Pütün, E., Tolay, M., Ekinci, E., "Seyitömer Bitümlü Şistlerinin Mineral Asit Ekstraksiyonu ile Zenginleştirilmesi", www.maden.org.tr
- [17] Kouassi, S.S., Tognonvi, M. T., Soro, J., Rossignol, S., "Consolidation mechanism of materials obtained from sodium silicate solution and silica-based aggregates", *Journal of Non-Crystalline Solids*, Vol. 357, pp. 3013-3022, May 2011
- [18] Glasser, F.P., "Chemistry of Alkali-Aggregate Reaction", *The Alkali-Silica Reaction in Concrete*, R.N. Swamy (editor), Van Nostrand Reinhold, 1992, pp. 30-53
- [19] Adelman, J.G., Elouatik, S., Demopoulos, G.P., "Investigation of sodium silicate-derived gels as encapsulants for hazardous materials – The case of scorodite", *Journal of Hazardous Materials*, Vol. 292, pp. 108-117, March 2015
- [20] Sarawade, P. B., Kim, J., Hilonga, A., Quang, D. V., Kim, H. T., "Effect of drying technique on the physicochemical properties of sodium silicate-based mesoporous precipitated silica", *Applied Surface Science*, Vol. 258, pp. 955-961, September 2011



Senay BALBAY: I am a Instructor of Vocational School, Department of Chemical and Chemical Process Technologies of Bilecik Seyh Edebali University in Turkey. I am a PhD student in Chemical Engineering Department of Bilecik Şeyh Edebali University, in Turkey. In Pamukkale University, I completed my masters degree in Environmental Engineering department. I graduated in Chemical Engineering Department of Eskişehir Osmangazi University. I worked in the automotive and white goods sectors.